

# Heterogeneous Elasto-plasticity


*πλάσσειν*

G. F. & Alessandro Giacomini

# Small strain elastoplasticity


## Small strain elasto-plasticity – the rheology

- A model with brake and spring:

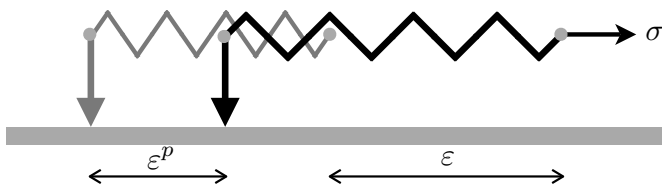

$$\text{with } \begin{cases} |\sigma| \leq \sigma_c \\ \dot{\epsilon}^p \geq 0 & \sigma = \sigma_c \\ \dot{\epsilon}^p = 0 & |\sigma| < \sigma_c \\ \dot{\epsilon}^p \leq 0 & \sigma = -\sigma_c \end{cases}$$

- Response:

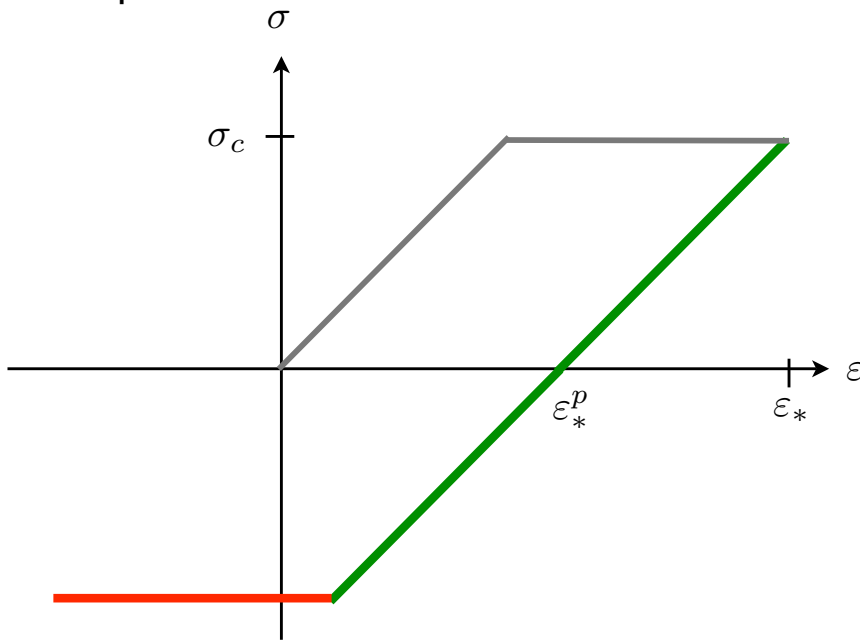

## Small strain elasto-plasticity – the formulation $\varepsilon^p \equiv p$

$$\mathbb{M}_{dev}^{N \times N} := \{\tau \text{ symmetric} : \text{tr } \tau = 0\}$$

$$\tau = \frac{\text{tr } \tau}{N} \mathbf{i} + \tau_D$$

- $Eu := \frac{Du + Du^t}{2} = e + p$

$$p \in \mathbb{M}_{dev}^{N \times N}$$

$$\sigma = Ae; \text{div } \sigma = 0 \quad \text{in } \Omega$$

$A$  : Hooke's law

$$\sigma \in K := \{\tau : f(\tau_D) \leq 0\}$$

with  $K$  closed convex

$$(f \text{ conv.}, f(0) < 0, f \xrightarrow{|\tau| \nearrow \infty} \infty)$$

set of admissible stresses

## Small strain elasto-plasticity – the formulation $\varepsilon^P \equiv p$

$$\mathbb{M}_{dev}^{N \times N} := \{ \tau \text{ symmetric} : \text{tr } \tau = 0 \}$$

$$\tau = \frac{\text{tr } \tau}{N} \mathbf{i} + \tau_D$$

$$\bullet \quad Eu := \frac{Du + Du^t}{2} = e + p$$

$$p \in \mathbb{M}_{dev}^{N \times N}$$

$$\sigma = Ae; \quad \text{div } \sigma = 0 \quad \text{in } \Omega$$

$A$ : Hooke's law

• Flow rule:

$$\dot{p}(t) \in \mathcal{A}\sigma :=$$

$$\left\{ \tau \in \mathbb{M}_{dev}^{N \times N} : \exists \lambda \geq 0 \text{ s.t. } \tau = \lambda \frac{\partial f}{\partial \tau}(\sigma(t)) \text{ and } \lambda f(\sigma(t)) = 0 \right\}$$



$$\dot{p}(t) \in N_K(\sigma(t)), \text{ the normal cone to } K \text{ at } \sigma(t) \in \partial K(t)$$

$$\sigma \in K := \{ \tau : f(\tau_D) \leq 0 \}$$

with  $K$  closed convex

$$(f \text{ conv.}, f(0) < 0, f \xrightarrow{|\tau| \nearrow \infty} \infty)$$

set of admissible stresses

## Small strain elasto-plasticity – the formulation $\varepsilon^P \equiv p$

$$\mathbb{M}_{dev}^{N \times N} := \{\tau \text{ symmetric} : \text{tr } \tau = 0\}$$

$$\tau = \frac{\text{tr } \tau}{N} \mathbf{i} + \tau_D$$

$$\bullet \quad Eu := \frac{Du + Du^t}{2} = e + p$$

$$p \in \mathbb{M}_{dev}^{N \times N}$$

$$\sigma = Ae; \quad \text{div } \sigma = 0 \quad \text{in } \Omega$$

$A$  : Hooke's law

• **Flow rule:**

$$\dot{p}(t) \in \mathcal{A}\sigma :=$$

$$\left\{ \tau \in \mathbb{M}_{dev}^{N \times N} : \exists \lambda \geq 0 \text{ s.t. } \tau = \lambda \frac{\partial f}{\partial \tau}(\sigma(t)) \text{ and } \lambda f(\sigma(t)) = 0 \right\}$$



$\dot{p}(t) \in N_K(\sigma(t))$ , the normal cone to  $K$  at  $\sigma(t) \in \partial K(t)$

• b.c. :  $u(x, t) = w(x, t) \in AC([0, T]; H^{\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^3))$

$\partial_d \Omega$  Dirichlet bdy: open /  $\partial_t \Omega := \partial \Omega \setminus \overline{\partial_d \Omega}$  : open, no forces

## Small strain elasto-plasticity – the formulation $\varepsilon^p \equiv p$

$$\mathbb{M}_{dev}^{N \times N} := \{\tau \text{ symmetric} : \text{tr } \tau = 0\}$$

$$\tau = \frac{\text{tr } \tau}{N} \mathbf{i} + \tau_D$$

$$\bullet \quad Eu := \frac{Du + Du^t}{2} = e + p$$

$$\sigma \in K := \{\tau : f(\tau_D) \leq 0\}$$

with  $K$  closed convex

$$p \in \mathbb{M}_{dev}^{N \times N}$$

$$\sigma = Ae; \quad \text{div } \sigma = 0 \quad \text{in } \Omega$$

$$(f \text{ conv.}, f(0) < 0, f \xrightarrow{|\tau| \nearrow \infty} \infty)$$

$A$ : Hooke's law

set of admissible stresses

• Flow rule:

$$\dot{p}(t) \in \mathcal{A}\sigma :=$$

$$\left\{ \tau \in \mathbb{M}_{dev}^{N \times N} : \exists \lambda \geq 0 \text{ s.t. } \tau = \lambda \frac{\partial f}{\partial \tau}(\sigma(t)) \text{ and } \lambda f(\sigma(t)) = 0 \right\}$$



$\dot{p}(t) \in N_K(\sigma(t))$ , the normal cone to  $K$  at  $\sigma(t) \in \partial K(t)$

• b.c. :  $u(x, t) = w(x, t) \in AC([0, T]; H^{\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^3))$

$\partial_d \Omega$  Dirichlet bdy: open /  $\partial_t \Omega := \partial \Omega \setminus \overline{\partial_d \Omega}$ : open, no forces

• Existence of an evolution known under  $C^2$ -smoothness for  $\partial \Omega +$

$C^2$ -smoothness of  $\partial_{\partial \Omega}[\partial_d \Omega]$ : – by viscoplastic approx. (Suquet 1978)

– through var. evolutions (Dal Maso-

De Simone-Mora 2004)

ve



## Small strain elasto-plasticity – the formulation $\varepsilon^p \equiv p$

$$\mathbb{M}_{dev}^{N \times N} := \{ \tau \text{ symmetric} : \text{tr } \tau = 0 \}$$

$$\tau = \frac{\text{tr } \tau}{N} \mathbf{i} + \tau_D$$

$$\bullet \quad Eu := \frac{Du + Du^t}{2} = e + p$$

$$p \in \mathbb{M}_{dev}^{N \times N}$$

$$\sigma = Ae; \quad \text{div } \sigma = 0 \quad \text{in } \Omega$$

$A$ : Hooke's law

• **Flow rule:**

$$\dot{p}(t) \in \mathcal{A}\sigma :=$$

$$\left\{ \tau \in \mathbb{M}_{dev}^{N \times N} : \exists \lambda \geq 0 \text{ s.t. } \tau = \lambda \frac{\partial f}{\partial \tau}(\sigma(t)) \text{ and } \lambda f(\sigma(t)) = 0 \right\}$$

$\Updownarrow$

$\dot{p}(t) \in N_K(\sigma(t))$ , the normal cone to  $K$  at  $\sigma(t) \in \partial K(t)$

• b.c. :  $u(x, t) = w(x, t) \in AC([0, T]; H^{\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^3))$

$\partial_d \Omega$  Dirichlet bdy: open /  $\partial_t \Omega := \partial \Omega \setminus \overline{\partial_d \Omega}$ : open, no forces

$$E(u) = e + p \text{ kin. compatibility } \begin{cases} u \in AC(0, T; BD(\Omega)) \\ e \in AC(0, T; L^2(\Omega; \mathbb{R}^N)) \\ p \in AC(0, T; \mathcal{M}_b(\Omega \cup \partial_d \Omega; \mathbb{M}_{dev}^{N \times N})) \end{cases}$$

$$\sigma \in K := \{ \tau : f(\tau_D) \leq 0 \}$$

with  $K$  closed convex

$$(f \text{ conv.}, f(0) < 0, f \xrightarrow{|\tau| \nearrow \infty} \infty)$$

set of admissible stresses



## Small strain elasto-plasticity – the formulation $\varepsilon^p \equiv p$

$$\mathbb{M}_{dev}^{N \times N} := \{ \tau \text{ symmetric} : \text{tr } \tau = 0 \}$$

$$\tau = \frac{\text{tr } \tau}{N} \mathbf{i} + \tau_D$$

$$\bullet \quad Eu := \frac{Du + Du^t}{2} = e + p$$

$$\sigma \in K := \{ \tau : f(\tau_D) \leq 0 \}$$

with  $K$  closed convex

$$p \in \mathbb{M}_{dev}^{N \times N}$$

$$\sigma = Ae; \quad \text{div } \sigma = 0 \quad \text{in } \Omega$$

$$(f \text{ conv.}, f(0) < 0, f \xrightarrow{|\tau| \nearrow \infty} \infty)$$

$A$ : Hooke's law

set of admissible stresses

• Flow rule:

$$\dot{p}(t) \in \mathcal{A}\sigma :=$$

$$\left\{ \tau \in \mathbb{M}_{dev}^{N \times N} : \exists \lambda \geq 0 \text{ s.t. } \tau = \lambda \frac{\partial f}{\partial \tau}(\sigma(t)) \text{ and } \lambda f(\sigma(t)) = 0 \right\}$$



$\dot{p}(t) \in N_K(\sigma(t))$ , the normal cone to  $K$  at  $\sigma(t) \in \partial K(t)$

• b.c. :  $u(x, t) = w(x, t) \in AC([0, T]; H^{\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^3))$

$\partial_d \Omega$  Dirichlet bdy: open /  $\partial_t \Omega := \partial \Omega \setminus \overline{\partial_d \Omega}$  : open, no forces

b.c. on  $\partial_d \Omega$  has been relaxed:  $p = [w - u] \odot \nu, w - u \perp \nu$

## A remark about stress admissibility – Lipschitz domain $\Omega$

- From  $\operatorname{div} \sigma = 0 + \sigma \in L^2(\Omega; \mathbb{M}_{sym}^{N \times N} \cap K)$ , we get:

$$(\sigma_D \nu)_\tau \text{ (the tangential part of } \sigma \nu) \in (K \nu)_\tau$$

↑ a priori well defined as an element of  $H_{00}^{-\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^N)$

## A remark about stress admissibility – Lipschitz domain $\Omega$

- From  $\operatorname{div} \sigma = 0 + \sigma \in L^2(\Omega; \mathbb{M}_{sym}^{N \times N} \cap K)$ , we get:

$$(\sigma_D \nu)_\tau \text{ (the tangential part of } \sigma \nu) \in (K \nu)_\tau$$

↑ a priori well defined as an element of  $H_{00}^{-\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^N)$

↓

- Since  $\dot{p} = [\dot{w}(t) - \dot{u}(t)] \odot \nu$  on  $\partial_d \Omega$ , with  $[\dot{w}(t) - \dot{u}(t)] \perp \nu$ , we expect a **boundary** flow rule:

$$[\dot{w}(t) - \dot{u}(t)] \in N_{(K \nu)_\tau}((\sigma_D \nu)_\tau) \text{ on } \partial_d \Omega$$

in fact well defined as an element of  $L^\infty(\partial_d \Omega; \mathbb{R}^N)$  ↑ maybe not unique  
unless bdy is  $C^2$

## A remark about stress admissibility – Lipschitz domain $\Omega$

- From  $\operatorname{div} \sigma = 0 + \sigma \in L^2(\Omega; \mathbb{M}_{sym}^{N \times N} \cap K)$ , we get:

$$(\sigma_D \nu)_\tau \text{ (the tangential part of } \sigma \nu) \in (K \nu)_\tau$$

↑ a priori well defined as an element of  $H_{00}^{-\frac{1}{2}}(\partial_d \Omega; \mathbb{R}^N)$

↓

- Since  $\dot{p} = [\dot{w}(t) - \dot{u}(t)] \odot \nu$  on  $\partial_d \Omega$ , with  $[\dot{w}(t) - \dot{u}(t)] \perp \nu$ , we expect a **boundary** flow rule:

$$[\dot{w}(t) - \dot{u}(t)] \in N_{(K \nu)_\tau}((\sigma_D \nu)_\tau) \text{ on } \partial_d \Omega$$

in fact well defined as an element of  $L^\infty(\partial_d \Omega; \mathbb{R}^N)$  ↑ maybe not unique  
unless bdry is  $C^2$

↑

bulk flow rule

# The variational approach to elastoplasticity

## Variational evolution in a nutshell

- Define:

- diss. pot. :  $H(p) := \sup\{\sigma_D \cdot p : \sigma \in K\}$

- dissipation:  $\mathcal{H}(q) := \int_{\Omega \cup \partial_d \Omega} H\left(\frac{q}{|q|}(x)\right) d|q|$

- total diss.:  $\mathcal{D}(0, t; p) := \sup_{part. \text{ of } [0, t]} \sum_i \mathcal{H}(p(t_{i+1}) - p(t_i))$

- total energy:  $E(t) := 1/2 \int_{\Omega} Ae(t) \cdot e(t) dx + \mathcal{D}(0, t; p)$

At each time  $t$ ,  $(u(t), e(t), \sigma(t) := Ae(t), p(t))$  satisfies

- Global min.:  $1/2 \int_{\Omega} Ae(t) \cdot e(t) dx \leq 1/2 \int_{\Omega} A\eta \cdot \eta dx + \mathcal{H}(q - p(t))$   
(ve)

- Energy cons.:  $\frac{dE}{dt}(t) = \int_{\Omega} \sigma(t) \cdot E\dot{w}(t) dx$

## Variational evolution in a nutshell

- Define:

- diss. pot. :  $H(p) := \sup\{\sigma_D \cdot p : \sigma \in K\}$

- dissipation:  $\mathcal{H}(q) := \int_{\Omega \cup \partial_d \Omega} H\left(\frac{q}{|q|}(x)\right) d|q|$

- total diss.:  $\mathcal{D}(0, t; p) := \sup_{part. \text{ of } [0, t]} \sum_i \mathcal{H}(p(t_{i+1}) - p(t_i))$

- total energy:  $E(t) := 1/2 \int_{\Omega} Ae(t) \cdot e(t) dx + \mathcal{D}(0, t; p)$

At each time  $t$ ,  $(u(t), e(t), \sigma(t) := Ae(t), p(t))$  satisfies

- Global min.:  $1/2 \int_{\Omega} Ae(t) \cdot e(t) dx \leq 1/2 \int_{\Omega} A\eta \cdot \eta dx + \mathcal{H}(q - p(t))$   
(ve)

- Energy cons.:  $\frac{dE}{dt}(t) = \int_{\Omega} \sigma(t) \cdot E\dot{w}(t) dx$

- Proof through time discretisation: Find  $(u_i, e_i, p_i)$  kin. compatible solving

$$\min \left\{ 1/2 \int_{\Omega} Ae \cdot e dx + \mathcal{H}(p - p_{i-1}) \right\}$$

## Variational evolution in a nutshell

• Define:

– diss. pot. :  $H(p) := \sup\{\sigma_D \cdot p : \sigma \in K\}$

– dissipation:  $\mathcal{H}(q) := \int_{\Omega \cup \partial_d \Omega} H\left(\frac{q}{|q|}(x)\right) d|q|$

– total diss.:  $\mathcal{D}(0, t; p) := \sup_{\text{part. of } [0, t]} \sum_i \mathcal{H}(p(t_{i+1}) - p(t_i))$

– total energy:  $E(t) := 1/2 \int_{\Omega} Ae(t) \cdot e(t) dx + \mathcal{D}(0, t; p)$

At each time  $t$ ,  $(u(t), e(t), \sigma(t) := Ae(t), p(t))$  satisfies

• Global min.:  $1/2 \int_{\Omega} Ae(t) \cdot e(t) dx \leq 1/2 \int_{\Omega} A\eta \cdot \eta dx + \mathcal{H}(q - p(t))$   
**(ve)**

• Energy cons.:  $\frac{dE}{dt}(t) = \int_{\Omega} \sigma(t) \cdot E\dot{w}(t) dx$

• Proof through time discretisation: Find  $(u_i, e_i, p_i)$  kin.

compatible solving

$$\min \left\{ 1/2 \int_{\Omega} Ae \cdot e dx + \mathcal{H}(p - p_{i-1}) \right\}$$

- Note that, if  $(u, e, p)$  (resp.  $(u', e', p')$ ) min.  $1/2 \int_{\Omega} A\eta \cdot \eta dx + \mathcal{H}(q - p)$  (resp  $p'$ ), then

$$\|e' - e\|_{L^2} \leq C \left\{ \|Ew' - Ew\|_{L^2} + |p' - p|_{\Omega \cup \partial_d \Omega}^{\frac{1}{2}} \right\}$$



## Variational evolution in a nutshell

- Define:

- diss. pot. :  $H(p) := \sup\{\sigma_D \cdot p : \sigma \in K\}$

- dissipation:  $\mathcal{H}(q) := \int_{\Omega \cup \partial_d \Omega} H\left(\frac{q}{|q|}(x)\right) d|q|$

- total diss.:  $\mathcal{D}(0, t; p) := \sup_{part. \text{ of } [0, t]} \sum_i \mathcal{H}(p(t_{i+1}) - p(t_i))$

- total energy:  $E(t) := 1/2 \int_{\Omega} Ae(t) \cdot e(t) dx + \mathcal{D}(0, t; p)$

At each time  $t$ ,  $(u(t), e(t), \sigma(t) := Ae(t), p(t))$  satisfies

- Global min.:  $1/2 \int_{\Omega} Ae(t) \cdot e(t) dx \leq 1/2 \int_{\Omega} A\eta \cdot \eta dx + \mathcal{H}(q - p(t))$   
(ve)

- Energy cons.:  $\frac{dE}{dt}(t) = \int_{\Omega} \sigma(t) \cdot E\dot{w}(t) dx$

- Proof through time discretisation: Find  $(u_i, e_i, p_i)$  kin. compatible solving

$$\min \left\{ 1/2 \int_{\Omega} Ae \cdot e dx + \mathcal{H}(p - p_{i-1}) \right\}$$

- The lower semi-continuity of  $\mathcal{H}$  is ensured by Reshetnyak's lower semi-continuity theorem

## Variational evolution & classical formulation – 1

- Global minimality  $\Leftrightarrow -\mathcal{H}(q) \leq \int_{\Omega} Ae \cdot \eta \, dx \leq \mathcal{H}(-q)$   
 $\forall (v, \eta, q)$  kin. compat. with b.c.  $w = 0$   
 $\Downarrow$   
equilibrium + Neumann b.c. +  $\sigma \in K$

## Variational evolution & classical formulation – 1

- Global minimality  $\Leftrightarrow -\mathcal{H}(q) \leq \int_{\Omega} Ae \cdot \eta \, dx \leq \mathcal{H}(-q)$   
 $\forall (v, \eta, q)$  kin. compat. with b.c.  $w = 0$   
 $\Downarrow$   
equilibrium + Neumann b.c. +  $\sigma \in K$

- To go further, need to define the duality  $\langle \sigma_D, p \rangle$ .  
Not so clear because  $\sigma_D$  not continuous!

## Issues of duality

Here  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

- First define  $\langle \sigma_D, p \rangle$  as a distribution:

$$\langle \sigma_D, p \rangle(\varphi) = - \int_{\Omega} \varphi \sigma \cdot (e - Ew) \, dx - \int_{\Omega} \sigma \cdot [(u - w) \odot \nabla \varphi] \, dx$$

↑ OK since  $\sigma \in L^N$

## Issues of duality

Here  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

- First define  $\langle \sigma_D, p \rangle$  as a distribution:

$$\langle \sigma_D, p \rangle(\varphi) = - \int_{\Omega} \varphi \sigma \cdot (e - Ew) \, dx - \int_{\Omega} \sigma \cdot [(u - w) \odot \nabla \varphi] \, dx$$

↑ OK since  $\sigma \in L^N$

- Known result: If  $\partial\Omega$  is  $C^2$  and  $\partial_{\partial\Omega}[\partial_d\Omega]$  is a  $C^2$   $(N - 2)$ -hypersurface, then  $\langle \sigma_D, p \rangle$  is a finite Radon meas. on  $\mathbb{R}^N$   
([Kohn-Temam 1983](#))
- **Thm:**  $\Omega$  Lipschitz. Then  $\langle \sigma_D, p \rangle$  is a finite Radon meas. on  $\mathbb{R}^N \setminus \partial_{\partial\Omega}[\partial_d\Omega]$  and  $|\langle \sigma_D, p \rangle| \leq \|\sigma_D\|_{L^\infty} |p|$ ,  $\langle \sigma_D, p \rangle_a = \sigma_D \cdot p_a$

## Issues of duality

Here  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

- First define  $\langle \sigma_D, p \rangle$  as a distribution:

$$\langle \sigma_D, p \rangle(\varphi) = - \int_{\Omega} \varphi \sigma \cdot (e - Ew) dx - \int_{\Omega} \sigma \cdot [(u - w) \odot \nabla \varphi] dx$$

↑ OK since  $\sigma \in L^N$

- Known result: If  $\partial\Omega$  is  $C^2$  and  $\partial_{\partial\Omega}[\partial_d\Omega]$  is a  $C^2$   $(N - 2)$ -hypersurface, then  $\langle \sigma_D, p \rangle$  is a finite Radon meas. on  $\mathbb{R}^N$  (Kohn-Temam 1983)
- **Thm:**  $\Omega$  Lipschitz. Then  $\langle \sigma_D, p \rangle$  is a finite Radon meas. on  $\mathbb{R}^N \setminus \partial_{\partial\Omega}[\partial_d\Omega]$  and  $|\langle \sigma_D, p \rangle| \leq \|\sigma_D\|_{L^\infty} |p|$ ,  $\langle \sigma_D, p \rangle_a = \sigma_D \cdot p_a$
- Technical point: What do we need for  $\langle \sigma_D, p \rangle$  to be a finite Radon meas. on all of  $\mathbb{R}^N$ ?
- Open pb.: Can we prove this under the only assumption that e.g.  $\mathcal{H}^{N-2}(\partial_{\partial\Omega}[\partial_d\Omega]) < \infty$ ?

## Variational evolution & classical formulation – 2

- Just using the definition of the duality:

$$\langle \sigma_D, p \rangle_{\lfloor \partial_d \Omega} = (\sigma_D \nu)_\tau (w - u) \mathcal{H}_{\lfloor \partial_d \Omega}^{N-1}$$

↓

(Ineq) 
$$H \left( \frac{p}{|p|} \right) |p| \geq \langle \sigma_D, p \rangle \text{ as measures}$$

Here again  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

## Variational evolution & classical formulation – 2

- Just using the definition of the duality:

$$\langle \sigma_D, p \rangle_{|\partial_d \Omega} = (\sigma_D \nu)_\tau (w - u) \mathcal{H}_{|\partial_d \Omega}^{N-1}$$

↓

(Ineq) 
$$H \left( \frac{p}{|p|} \right) |p| \geq \langle \sigma_D, p \rangle \text{ as measures}$$

Here again  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

- From energy equality + Reshetnyak's lower semi-continuity thm.:  

$$\mathcal{H}(\dot{p}) \underset{\uparrow \text{l.s.c.}}{\leq} \dot{D}(0, t, p) = - \int_{\Omega} \sigma(t) \cdot (\dot{e} - E\dot{w})(t) dx \underset{\uparrow \text{en. eq.}}{=} \langle \sigma_D, \dot{p} \rangle (\Omega \cup \partial_d \Omega) \underset{\uparrow \text{duality}}{}$$



## Variational evolution & classical formulation – 2

- Just using the definition of the duality:

$$\langle \sigma_D, p \rangle_{\partial_d \Omega} = (\sigma_D \nu)_\tau (w - u) \mathcal{H}_{\partial_d \Omega}^{N-1}$$

↓

(Ineq) 
$$H \left( \frac{p}{|p|} \right) |p| \geq \langle \sigma_D, p \rangle \text{ as measures}$$

Here again  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

- From energy equality + Reshetnyak's lower semi-continuity thm.:

$$\mathcal{H}(\dot{p}) \leq \dot{D}(0, t, p) = - \int_{\Omega} \sigma(t) \cdot (\dot{e} - E\dot{w})(t) dx = \langle \sigma_D, \dot{p} \rangle(\Omega \cup \partial_d \Omega)$$

$\uparrow$  l.s.c.                       $\uparrow$  en. eq.     $\uparrow$  duality

↓

Hill's maximal plastic work principle

$$\langle \sigma_D, \dot{p} \rangle(\Omega \cup \partial_d \Omega) = \sup_{\tau_D \text{ adm.}} \langle \tau_D, \dot{p} \rangle(\Omega \cup \partial_d \Omega)$$

## Variational evolution & classical formulation – 2

- Just using the definition of the duality:

$$\langle \sigma_D, p \rangle_{\lfloor \partial_d \Omega} = (\sigma_D \nu)_\tau (w - u) \mathcal{H}_{\lfloor \partial_d \Omega}^{N-1}$$

↓

(Ineq) 
$$H \left( \frac{p}{|p|} \right) |p| \geq \langle \sigma_D, p \rangle \text{ as measures}$$

Here again  $\sigma$  and  $p$  are arbitrary provided that  $\sigma$  satisfies [eqm.](#) + [Neumann b.c.](#) + [stress adm.](#) &  $p$  is assd. to  $(u, e, p)$  kin. compatible with  $w$  as b.c.

- From energy equality + Reshetnyak's lower semi-continuity thm.:

$$\mathcal{H}(\dot{p}) \leq \dot{D}(0, t, p) = - \int_{\Omega} \sigma(t) \cdot (\dot{e} - E\dot{w})(t) dx = \langle \sigma_D, \dot{p} \rangle (\Omega \cup \partial_d \Omega)$$

↑ l.s.c.
↑ en. eq.
↑ duality

↓

Hill's maximal plastic work principle



$$\langle \sigma_D, \dot{p} \rangle (\Omega \cup \partial_d \Omega) = \sup_{\tau_D \text{ adm.}} \langle \tau_D, \dot{p} \rangle (\Omega \cup \partial_d \Omega)$$

- From  $H \left( \frac{\dot{p}}{|\dot{p}|} \right) |\dot{p}| = \langle \sigma_D, \dot{p} \rangle$ , we recover the flow rule, **BOTH** in  $\Omega$  and on  $\partial_d \Omega$ :

$$\dot{p}_a \in N_K(\sigma_D) \text{ in } \Omega; |\dot{w} - \dot{u}| \in N_{(K\nu)_\tau}((\sigma_D \nu)_\tau) \text{ on } \partial_d \Omega$$



# Heterogeneous elastoplasticity

## A multiphase domain

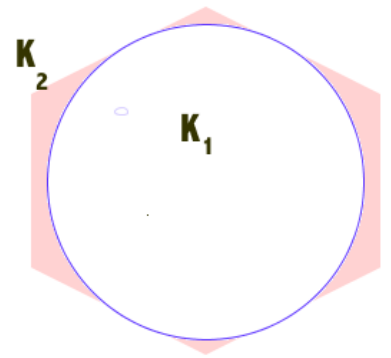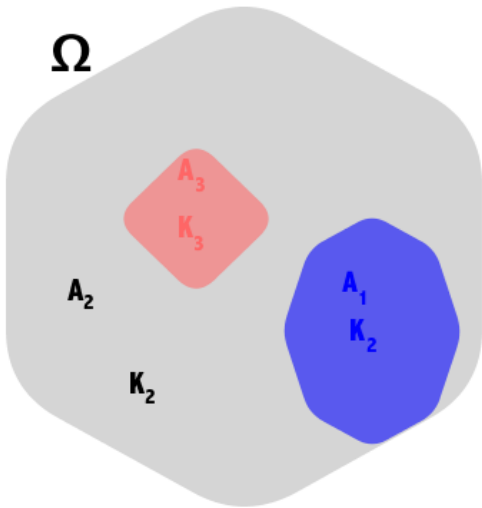

No ordering property of the  $K_i$ 's  
We will need  $C^1$  interfaces

## A multiphase domain

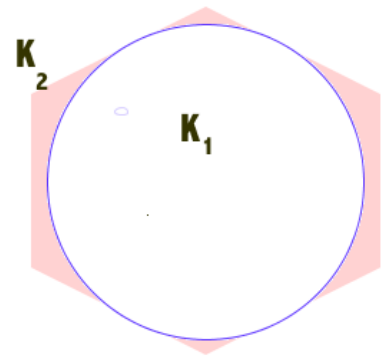
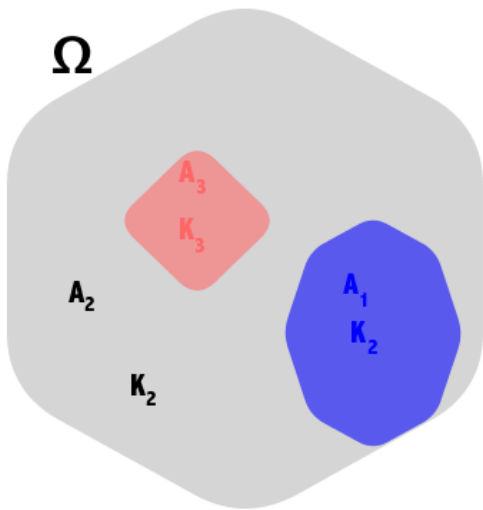


No ordering property of the  $K_i$ 's  
We will need  $C^1$  interfaces

- Define the dissipation :

$H(x, p) := H_i(p) = \sup\{\sigma_D \cdot p : \sigma_D \in K_i\}$  in each phase  $i$ . Since we expect  $p$  to be a measure, how do we define  $H$  on  $\bar{\Omega}_i \cap \bar{\Omega}_j$ ?

## A multiphase domain

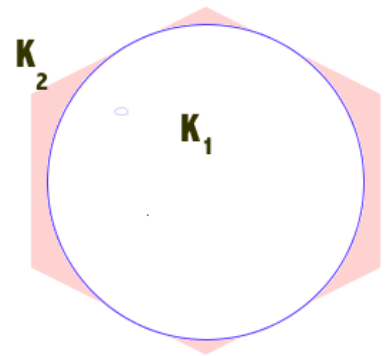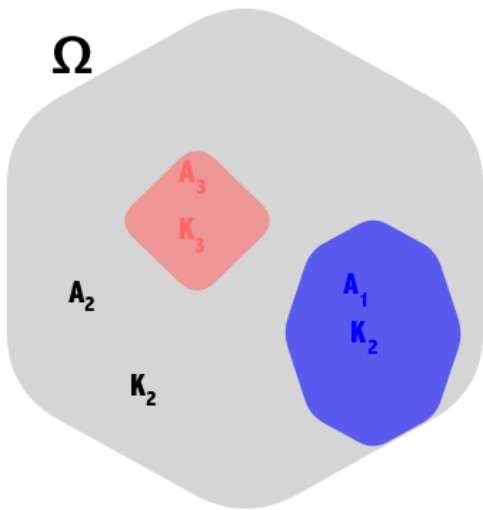

No ordering property of the  $K_i$ 's  
We will need  $C^1$  interfaces

- ~~$\mathcal{H}(a, b, H)$~~  because destroys convexity  $\Rightarrow$  **Inf-convolution:**

$$H(x, \xi) :=$$

$$\begin{cases} \inf\{H(a \odot \nu(x)) + H(-b \odot \nu(x)); a - b = c\}, & \text{if } \xi = c \odot \nu(x) \\ \infty, & \text{else} \end{cases}$$

$\Downarrow$

destroys l.s.c./ Need to re-establish l.s.c. of  $\mathcal{H}$ :

**Thm:** If  $(u_n, e_n, p_n)$  kin. compatible and the natural weak conv. hold  $(BD \times L^2 \times \mathcal{M}_b)$  then  $\mathcal{H}(p) \leq \liminf_n \mathcal{H}(p_n)$

-why  $C^1$ -interfaces are necessary  $\Rightarrow$

## Heterogeneous evolution

- Existence of a variational evolution
- We recover all results of homogeneous case + interfacial conditions:

## Heterogeneous evolution

- Existence of a variational evolution
- We recover all results of homogeneous case + interfacial conditions:
- **Stress adm.:**  $(\sigma_D \nu)_\tau \in (K_i \nu)_\tau \cap (K_j \nu)_\tau$



## Heterogeneous evolution

- Existence of a variational evolution
- We recover all results of homogeneous case + interfacial conditions:
- **Stress adm.:**  $(\sigma_D \nu)_\tau \in (K_i \nu)_\tau \cap (K_j \nu)_\tau$
- **Flow rule:**  $\dot{u}_i - \dot{u}_j \in N_{(K_i \nu)_\tau \cap (K_j \nu)_\tau}((\sigma_D \nu)_\tau)$
- Exact expression of  $H$  on interfaces is used in deriving ▶ (Ineq)

## Heterogeneous evolution

- Existence of a variational evolution
- We recover all results of homogeneous case + interfacial conditions:
- **Stress adm.:**  $(\sigma_D \nu)_\tau \in (K_i \nu)_\tau \cap (K_j \nu)_\tau$
- **Flow rule:**  $\dot{u}_i - \dot{u}_j \in N_{(K_i \nu)_\tau \cap (K_j \nu)_\tau}((\sigma_D \nu)_\tau)$
- Exact expression of  $H$  on interfaces is used in deriving ▶ (Ineq)

*For now unable to find concrete example where the interfacial flow rule makes a difference!*

## Heterogeneous evolution

- Existence of a variational evolution
- We recover all results of homogeneous case + interfacial conditions:
- **Stress adm.:**  $(\sigma_{D\nu})_\tau \in (K_i\nu)_\tau \cap (K_j\nu)_\tau$
- **Flow rule:**  $\dot{u}_i - \dot{u}_j \in N_{(K_i\nu)_\tau \cap (K_j\nu)_\tau}((\sigma_{D\nu})_\tau)$
- Exact expression of  $H$  on interfaces is used in deriving ▶ (Ineq)

*For now unable to find concrete example where the interfacial flow rule makes a difference!*

- Choice of dissipation is the right one for passing to the zero hardening limit in a model with isotropic linear hardening.

## Homogenization

- Rescaled heterogeneous variational evolution:  $x$  replaced by  $x/\varepsilon$  for multiphase torus  $\mathcal{Y}$  with  $C^1$  interfaces.
- Homogenization: with approp. i.c.'s,  $\exists \varepsilon_n$  s.t., for all  $t \in [0, T]$ ,

$$\begin{cases} u_n(t) \xrightarrow{*} u(t) & \text{weakly* in } BD(\Omega') \\ e_n(t) \xrightarrow{w-2} E(t) & \text{two-scale weakly in } L^2(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N}) \\ p_n(t) \xrightarrow{w^*-2} P(t) & \text{two-scale weakly* in } \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_D^N). \end{cases}$$

Here,  $E(x, y) \mathcal{L}_x^N \otimes \mathcal{L}_y^N + P - Eu \otimes \mathcal{L}_y^N = E_y \mu$  in  $\Omega' \times \mathcal{Y}$  with  $\mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{R}^N)$ ,  $E_y \mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N})$ ,  $\mu(F \times \mathcal{Y}) = 0$ ,  $\forall F$  Borel  $\subseteq \Omega'$ .

## Homogenization

- Rescaled heterogeneous variational evolution:  $x$  replaced by  $x/\varepsilon$  for multiphase torus  $\mathcal{Y}$  with  $C^1$  interfaces.
- Homogenization: with approp. i.c.'s,  $\exists \varepsilon_n$  s.t., for all  $t \in [0, T]$ ,

$$\begin{cases} u_n(t) \xrightarrow{*} u(t) & \text{weakly* in } BD(\Omega') \\ e_n(t) \xrightarrow{w-2} E(t) & \text{two-scale weakly in } L^2(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N}) \\ p_n(t) \xrightarrow{w^*-2} P(t) & \text{two-scale weakly* in } \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_D^N). \end{cases}$$

Here,  $E(x, y) \mathcal{L}_x^N \otimes \mathcal{L}_y^N + P - Eu \otimes \mathcal{L}_y^N = E_y \mu$  in  $\Omega' \times \mathcal{Y}$  with  $\mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{R}^N)$ ,  $E_y \mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N})$ ,  $\mu(F \times \mathcal{Y}) = 0$ ,  $\forall F$  Borel  $\subseteq \Omega'$ .

- Further  $(u(t), E(t), P(t))$  is a **two-scale quasistatic evolution**: defined as before with explicit  $y$ -dependence; for example:

$$\text{dissipation } \mathcal{H}^{hom}(Q) := \int_{\mathcal{Y} \times \Omega \cup \partial_d \Omega} H \left( y, \frac{Q}{|Q|}(x, y) \right) d|Q|$$

## Homogenization

- Rescaled heterogeneous variational evolution:  $x$  replaced by  $x/\varepsilon$  for multiphase torus  $\mathcal{Y}$  with  $C^1$  interfaces.
- Homogenization: with approp. i.c.'s,  $\exists \varepsilon_n$  s.t., for all  $t \in [0, T]$ ,

$$\begin{cases} u_n(t) \xrightarrow{*} u(t) & \text{weakly* in } BD(\Omega') \\ e_n(t) \xrightarrow{w-2} E(t) & \text{two-scale weakly in } L^2(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N}) \\ p_n(t) \xrightarrow{w^*-2} P(t) & \text{two-scale weakly* in } \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_D^N). \end{cases}$$

Here,  $E(x, y) \mathcal{L}_x^N \otimes \mathcal{L}_y^N + P - Eu \otimes \mathcal{L}_y^N = E_y \mu$  in  $\Omega' \times \mathcal{Y}$  with  $\mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{R}^N)$ ,  $E_y \mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N})$ ,  $\mu(F \times \mathcal{Y}) = 0$ ,  $\forall F$  Borel  $\subseteq \Omega'$ .

- Further  $(u(t), E(t), P(t))$  is a **two-scale quasistatic evolution**: defined as before with explicit  $y$ -dependence; for example:

$$\text{dissipation } \mathcal{H}^{hom}(Q) := \int_{\mathcal{Y} \times \Omega \cup \partial_d \Omega} H \left( y, \frac{Q}{|Q|}(x, y) \right) d|Q|$$

- Not possible to eliminate  $y$ -dependence

## Homogenization

- Rescaled heterogeneous variational evolution:  $x$  replaced by  $x/\varepsilon$  for multiphase torus  $\mathcal{Y}$  with  $C^1$  interfaces.
- Homogenization: with approp. i.c.'s,  $\exists \varepsilon_n$  s.t., for all  $t \in [0, T]$ ,

$$\begin{cases} u_n(t) \xrightarrow{*} u(t) & \text{weakly* in } BD(\Omega') \\ e_n(t) \xrightarrow{w-2} E(t) & \text{two-scale weakly in } L^2(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N}) \\ p_n(t) \xrightarrow{w^*-2} P(t) & \text{two-scale weakly* in } \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_D^N). \end{cases}$$

Here,  $E(x, y) \mathcal{L}_x^N \otimes \mathcal{L}_y^N + P - Eu \otimes \mathcal{L}_y^N = E_y \mu$  in  $\Omega' \times \mathcal{Y}$  with  $\mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{R}^N)$ ,  $E_y \mu \in \mathcal{M}_b(\Omega' \times \mathcal{Y}; \mathbb{M}_{sym}^{N \times N})$ ,  $\mu(F \times \mathcal{Y}) = 0$ ,  $\forall F$  Borel  $\subseteq \Omega'$ .

- Further  $(u(t), E(t), P(t))$  is a **two-scale quasistatic evolution**: defined as before with explicit  $y$ -dependence; for example:

$$\text{dissipation } \mathcal{H}^{hom}(Q) := \int_{\mathcal{Y} \times \Omega \cup \partial_d \Omega} H \left( y, \frac{Q}{|Q|}(x, y) \right) d|Q|$$

- Not possible to eliminate  $y$ -dependence
- In essence,  $P(\cdot, \cdot, y)$  is, for each  $y \in \mathcal{Y}$ , an internal var.  $\Rightarrow \exists$  flow rule in  $y$  that expresses normality at the micro level.....